

INFLUENCE OF MAGNETIC FIELD ON THE SLIDING OF STEEL AGAINST LUBRICATED POLYAMIDE

Zaini H.¹, Alahmadi A.¹, Abdel-Sattar S.¹ and Ali W. Y.²

¹Faculty of Engineering, Taif University, Al-Taif, SAUDI ARABIA.

²Current Address: Faculty of Engineering, Minia University, El-Minia, EGYPT.

ABSTRACT

The present work investigates the influence of magnetic field on the friction coefficient displayed by sliding of steel pin on polyamide disc lubricated by paraffin oil and dispersed by different lubricant additives such as zinc dialkyldithiophosphates (ZDDP), molybdenum disulphide (MoS₂), heteropolar organic based additive (CMOC), graphite (C), detergent additive (calcium sulphonate) (DA), polytetrafluoroethylene (PTFE) and polymethyl methacrylate (PMMA).

Based on the experiments carried out in the present work, it was found that, at surfaces lubricated by paraffinic molecules friction coefficient decreased with increasing applied load. As the magnetic field increased friction coefficient increased. When the oil was dispersed by ZDDP additive significant decrease of friction was observed. The performance of ZDDP additive was not affected by application of the magnetic field. Dispersing Mo S₂ or C in the lubricating oil caused significant friction increase. The effect of magnetic field on performance of MoS₂ was insignificant, while magnetic field caused slight friction reduction in the presence of C. Magnetic field decreased friction coefficient when the oil was dispersed by CMOC. Under the action of magnetic field the force of adhesion significantly increased causing proper surface coating which caused the friction decrease. Oil dispersed by calcium sulphonate showed significant friction decrease due to the polarity of its molecules. Application of magnetic field caused further friction decrease. As a result of the quite good response of DA additive with magnetic field based on the values of friction coefficient observed for the oil dispersed by DA additive, it can be recommended to use this additive when magnetic field is applied. The good lubricating properties observed for PTFE additive can be from its ability to form a layer on the sliding surfaces. PTFE particles dispersed in the oil were much influenced by magnetic field, where the lowest value was displayed at the highest intensity of magnetic field. The same trend of friction decrease was observed for PMMA particles dispersed in oil.

KEYWORDS

Magnetic field, friction coefficient, steel, polyamide, oil additives, polytetrafluoroethylene, polymethyl methacrylate, molybdenum disulphide, zinc dialkyldithiophosphates and graphite.

INTRODUCTION

Magnetic fields are generated in various mechanical and electronic devices. It is important to consider the friction and wear of their components and to understand the influence of magnetic field on their performance in order to prevent premature failure and to achieve higher energy efficiency. The effect of magnetic field on friction and wear processes has been studied by a number of researchers. It was observed a significant transformation in tool wear tests with the magnetic field, [1 - 6]. Abrasive wear without magnetic fields was transformed, in the presence of magnetic field, to fracture due to the shift of shear stress to the subsurface region. Also, a decrease in wear, a lower friction coefficient, increase in hardness of magnetised steel surface and a rise in temperature of rubbing surfaces were observed. In magnetic fields, strongly oxidised wear particles will pose a serious problem for the contact due to the paramagnetism of oxygen. Accelerated oxidation does affect not only wear particles but also contacting surfaces. More specifically, highly oxidised wear particles, affected by magnetic force operating between contacting surfaces, act both as abrasive and as lubricating agents depending on their conditions.

It was observed that, for sliding of steel pin against oil lubricated brass discs, magnetic field decreased friction coefficient for all the tested oils, [7]. Dispersing oil by polyethylene (PE) particles significantly increased friction coefficient. A drastic reduction of friction coefficient was observed for olive, castor and almonds oils, when dispersing the tested oils by polyamide (PA) particles. Sliding of steel pin on oil lubricated aluminium disc caused significant friction increase for all the tested oils. Drastic friction reduction was observed for castor, almonds, jasmine and camomile oils when dispersed by PE particles. Dispersing vegetable oils by PA particles showed relatively lower friction coefficient for olive and castor oils, while corn, almonds, camomile and jasmine oils showed relatively higher friction values. Sliding of steel pin on oil lubricated steel disc showed the highest values of friction coefficient. Dispersing the tested oils by PE particles did not decrease friction coefficient. Jasmine oil displayed relatively lower friction than the other tested oils.

The effect of magnetic field on the friction coefficient displayed by sliding of steel pin against steel disc lubricated by paraffin oil and dispersed by different lubricants additives was investigated, [8]. The experiments showed that, friction coefficient increased as the magnetic field increased due to the increase of the normal load caused by the magnetic force. The performance of ZDDP and Mo S₂ additives was not affected by the application of magnetic field. Besides, it was observed that magnetic field much affected the performance of oil dispersed by additives of electrical properties such as CMOC, DA and PTFE particles. The same trend of friction decrease was observed for PMMA particles dispersed in oil.

The friction and wear of polyethylene sliding against steel in the presence of magnetic field was investigated, [9]. It was found that, application of magnetic field decreases friction coefficient at dry sliding due to its influence to decrease the adherence of polyethylene worn particles into the steel counterface. Besides, the magnetic field favors the formation of oxide film on the contact surface, where it plays a protective role in dry friction, modifies the friction and changes wear from severe wear to mild. Lubricating the steel surface by oils caused significant reduction in friction coefficient, where the

maximum reduction was displayed by paraffin followed by glycerine, almond, jasmine, corn, castor, olive and sun flower oils. Besides, wear of polyethylene test specimens shows relative decrease in the presence of magnetic field.

The effect of the magnetic field on the friction and wear of steel and brass sheets scratched by a steel insert at dry, lubricated by vegetable oils and dispersed by polymeric particles such as high density polyethylene (HDPE), polyamide (PA6) and polymethyl methacrylate (PMMA) was investigated, [10, 11]. Based on the experimental observations, it was found that olive oil displayed the lowest values of friction coefficient followed by castor oil, almonds, corn, chamomile and jasmine oils, where their polar molecules could significantly improve the wear resistance developed by their strong adsorption on the sliding surfaces. Application of magnetic field on the sliding surface caused significant friction reduction at dry sliding due to the enhanced ability of the oil molecules to orient themselves in relatively long chain adhered to the sliding surface and thus decreased the friction and wear.

The effect of applying external voltage on the sliding of copper, aluminium and polyethylene against steel surface lubricated by paraffin oil dispersed by polymeric particles such as polyethylene, polyamide and PMMA was tested, [12]. It was noticed that the friction coefficient and wear were significantly influenced by the generation of electric static charge on the contact surfaces which caused an attractive force imposed to the normal load. It was found that wear was more influenced by the electric static charge than friction coefficient.

It was shown that the magnetic field had no effect on friction coefficient observed for lithium grease without additives, [13]. Grease dispersed by high density polyethylene showed friction decrease. The lowest friction reduction was observed for polymethyl methacrylate. The strong adhesion of PTFE particles into the sliding surfaces significantly increased friction coefficient. It seems that PTFE particles were adhered to surfaces of inner and outer races as well as the balls. Changing the terminal of the voltage applied to the rotating shaft caused significant friction decrease for PMMA. Viscosity of the grease decreased with increasing the voltage. Friction coefficient decreased for HDPE and PTFE. The lowest friction values were observed at 6 volts which indicated that increasing voltage across the sliding surface could significantly decrease friction coefficient.

In the presence of magnetic field around the tribocontact and in ambient air, the contact track was covered with very fine ferromagnetic particles, [14]. Friction and wear are influenced by the presence of oxide. The increase of oxide layer on the surface, the retention of passivated particles in the contact and their refinement by grinding modify the contact rheology which transits from metal/metal contact to oxide/oxide contact. It was noticed that magnetic field acts on the ferromagnetic contact surface by modifying their electrical and electronic behaviour. It increases the electronic speed in their orbits, [15], and creates the electrical fields and the electrical currents. Those electrical currents enhance the oxidation. Moreover, dislocations in subsurface of the materials in contact are influenced by contact shear stress field [16]. The stress field presents a decreasing gradient from the Hertzian point. The dislocations displace from the region of strong stress gradient to the region of weak gradient. The existence of magnetic field around the contact facilitates the movement of dislocations due to mechanical stress, decreasing

the obstacles through the rearrangement of magnetic domains. This accumulation of dislocations leads to the increase of surface hardness.

From the analyses of experimental data, it is shown that in presence of active gases, the oxide layer growth and the transferred graphite films on the steel track are enhanced by a magnetic field. The graphite layer possesses good adhesion to the steel surface and leads to the best reduction of wear and friction coefficient, [17, 18]. However, when the friction test is operated in inert environment and in presence of a magnetic field, the opposed phenomenon is observed. The transfer of harder steel to softer graphite surface is responsible for the increase of friction and wear. This abnormal process is due to a magnetization of ferromagnetic steel which is known to be accompanied by reduction of plasticity and increasing the brittleness, [19]. It is known that, during friction on metals or dielectric couples, part of the energy consumed turns into electrical energy. In the second part of the study, electrical phenomena induced by friction will be examined in situ. Hence, the appearance of the potential difference generated by lubricated friction will be studied. This electrical effect leads to an embrittlement of friction surfaces and also involves a greater reactivity of surfaces with the lubricant. Indeed, stress corrosion cracking, and hydrogen embrittlement have been described in similar terms. Hence, an externally applied voltage may modify the wear behaviour of the lubricant and also, without friction, its decomposition and its reactivity on the surface; we shall try to analysis these effects in this paper, [20]. Because of triboelectrification, the charged surfaces can interact with each other due to the direct electrostatic forces, [21]. Since these forces are strong and effective, they contribute a major part of the adhesion force.

By applying an electric field between the rubbing surfaces, the oxidation of the rubbing surface at anode side is enhanced, and suppressed on the cathode side surface. The oxide film formed on the anode surface being harder than the bulk steel, the rubbing surface at the anode side was little worn, but it at cathode side was abrasively worn considerably. The application of an electric field, however, is considered to promote the breakdown of EHL film formed. Therefore, the effect of the application of an electric condition tested, [22]. The influence of applying electric field on the tribological behaviour of steel in a vertical magnetic field produced by an AC or DC electric current was investigated. The effect of a magnetic field on both oxidation and concentrations of dislocations on the surface is presented, [23]. Experiments show that a magnetic field applied through the sliding contact leads to decrease the wear rate.

In the present work, the effect of magnetic field on the friction coefficient displayed by sliding of steel pin against polyamide disc lubricated by paraffin oil and dispersed by different lubricants additives is investigated.

EXPERIMENTAL

Experiments were carried out using pin-on-disc wear tester. It consists of a rotary horizontal steel disc driven by variable speed motor. The details of the wear tester are shown in Fig. 1. The bearing steel pin (AISI 52100) is held in the specimen holder that fastened to the loading lever. Friction force can be measured by means of the load cell, where the pin holder and magnetic field were assembled. The polyamide disc was fastened to the rotating disc. Its surface roughness was about $6.7 \mu\text{m}$, R_a . Test specimens were rollers of cylindrical rolling bearing in the form of cylindrical pins of 6 mm diameter and 12 mm length. Friction and wear tests were carried out under constant

sliding velocity of 2.0 m/s and 20 N applied load. Every experiment lasted 30 minutes. All measurements were performed at 25 ± 5 °C and 30 ± 10 % humidity.

The lubricant used in the experiments was paraffin oil (SAE 30). Fine particles of C, MoS₂ and CMOC of particle size less than 1.0 μm were dispersed into the paraffin oil at 5.0 wt. % concentration. Besides, ZDDP and detergent additive (calcium sulphonate) were used. Polymeric powder such as PTFE and PMMA of (30 – 50 μm) particle size were used as dispersant in the oil. Magnetic field was applied by a coil assembled above the pin holder of 0.2 and 0.4 mG flux intensity, Fig. 2.

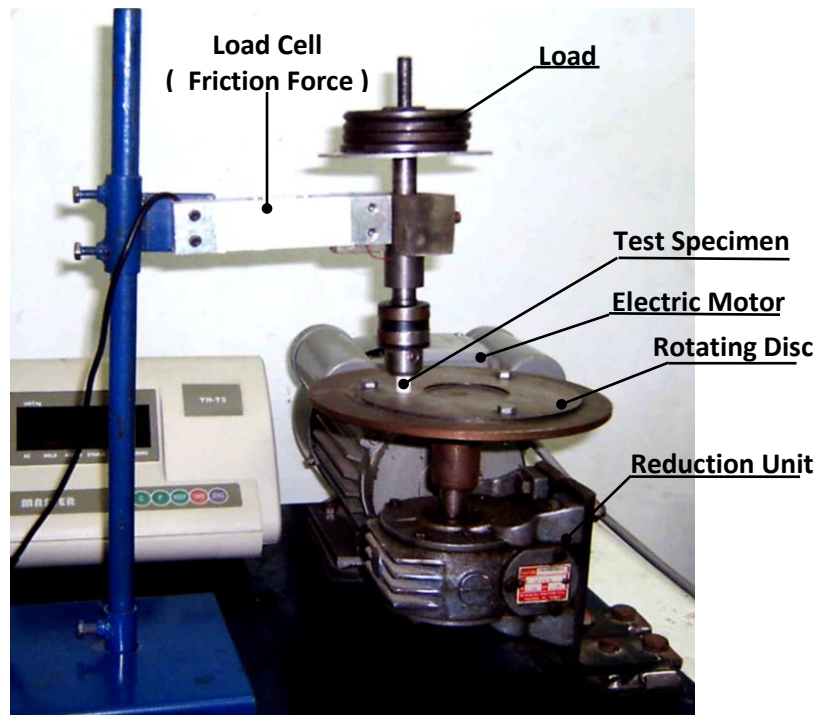


Fig. 1 Arrangement of the test rig.

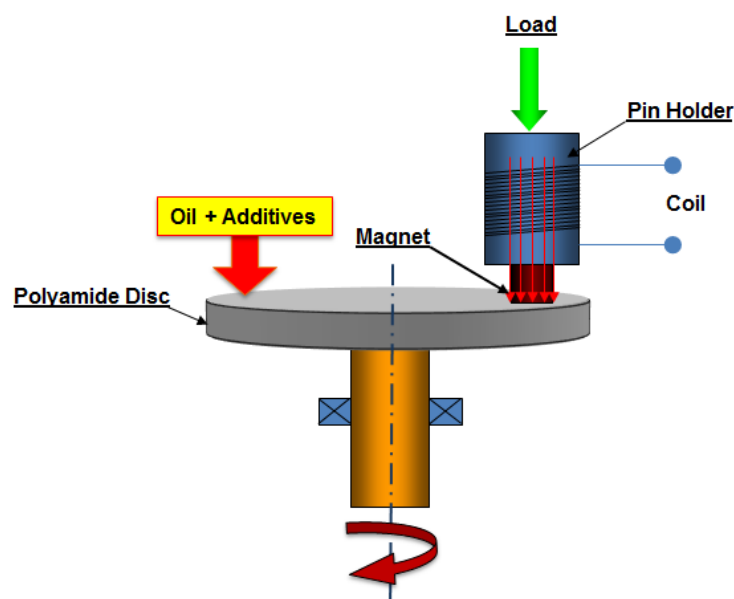


Fig. 2 Application of the magnetic field.

RESULTS AND DISCUSSION

The friction coefficient displayed by the steel pin sliding against polyamide disc under application of magnetic field is discussed, Figs. 3 - 10. Friction coefficient displayed by the sliding of steel pin against oil lubricated polyamide disc is shown in Fig. 3. Friction coefficient slightly decreased with increasing applied load. Based on the sliding velocity and load the sliding was considered as mixed lubrication, where the contact was mixed lubrication (partially metal to metal and partially hydrodynamic film). Therefore, friction decrease might be attributed to the plastic deformation of the asperities of the contact surface as well as the frictional heating so that the yield shear strength decreased. The effect of magnetic field on the performance of paraffin oil depends on the paraffinic molecules which are approximately linear and consequently they are more effective than other hydrocarbons in preventing solid contact. This allows for the formation and persistence of a relatively thicker film. Since the molecules are polar the opposite ends are attracted to form pairs of molecules which are subsequently incorporated into the viscous surface layer. At the interface with the substrate the attractive force of the free end of the molecules to the substrate is sufficient to firmly bond the entire layer. The presence of polar groups in oil structure enhanced the orientation of oil molecules to form a surface film able to inhibit metal-to-metal contact. This behaviour leads to the friction decrease. Although polyamide is not a magnetic material, as the magnetic field increased friction coefficient slightly increased. Sliding of steel against polyamide charged the contact surfaces so that they could interact with each other due to the direct electrostatic forces. Since these forces are strong and effective, they contribute a major part of the adhesion force.

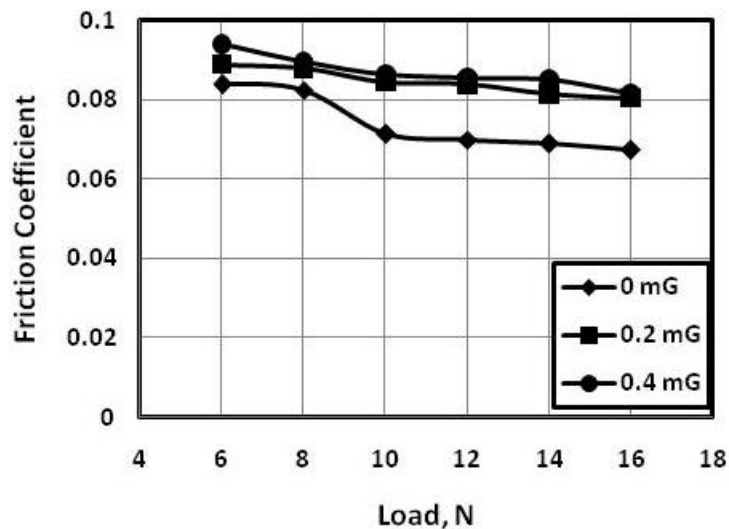


Fig. 3 Friction coefficient displayed by the sliding of steel pin against oil lubricated polyamide disc.

It is well known that a magnetic field affects polar molecules, which contain ionisable groups. The observed changes in the properties of polymers are attributed to the catalytic effect of the magnetic field on the molecules. The ability of polymers to reduce friction depends on their adherence to the sliding surfaces. The friction of the polymers with the steel surfaces produces electric static charge on both the surfaces of polymers

and steel. The sign and amount of the charge depends on the location of the polymeric materials and steel in the triboelectric series. When two different materials are pressed or rubbed together, the surface of one material will generally gain some electrons from the surface of the other material. The material that gains electrons has the stronger affinity for negative charge of the two materials, and that surface will be negatively charged after the materials are separated. The other material will have an equal amount of positive charge. The amount and polarity of the charge on each surface can be measured for insulating materials. The triboelectric series predict which will become positive or negative and how strong the electric charge will be.

Dispersing oil by ZDDP additive caused significant friction decrease due to its decomposition to zinc polyphosphate and a mixture of alkyl sulphides which are the precursors of the antiwear action of ZDDP, Fig. 4. Zinc phosphate reacts with the surface oxide layer by physical absorption and FeS is formed via the oxide layer and elemental sulphur generated from alkyl sulphides with Fe_2O_3 . It is hypothesized that their presence there as fusible glassy compounds, phosphorus as polyphosphate and iron sulphide as a ternary eutectic, provides the antiwear action of ZDDP. The formation of the glassy layer on the steel surface was responsible for the friction decrease, where oil film covered most of the contact area. The performance of ZDDP additive was not affected by application of the magnetic field. The values of friction coefficient were much higher than that displayed by sliding steel pin against steel disc, [8]. This behaviour confirmed that the influence of magnetic field can not be reduced in only increasing the applied load by the extra magnetic force superimposed on it. It seems that magnetic field also strengthened the adhesion of the oil film into the sliding surface so that the area of hydrodynamic lubrication increased leading to the decrease of friction coefficient. Friction coefficient displayed by the sliding of steel pin against oil lubricated polyamide disc showed relatively higher values in the presence of the magnetic field. The friction increase might be from the electrostatic charge generated from the friction of steel on polyamide.

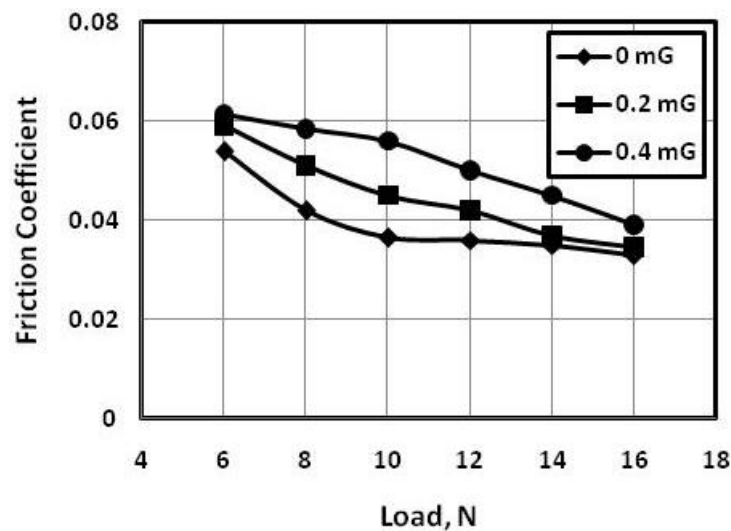


Fig. 4 Friction coefficient displayed by the sliding of steel pin against polyamide disc lubricated by oil dispersed by ZDDP.

Friction coefficient displayed by the sliding of steel pin against polyamide disc lubricated by oil dispersed by MoS₂ is shown in Fig. 5. Friction coefficient showed relatively lower values in the presence of the magnetic field than that displayed by steel pin sliding against steel disc. The friction decrease might be from the common good lubricating properties of MoS₂. Under the influence of moving surfaces, aggregates are disrupted and the solid MoS₂ fills in the pits and valleys, thereby reducing roughness, increasing the true area of contact and providing a reservoir of lubricant, its drawback, as an antiwear additive dispersed in oil, is in its insolubility which causes flocculation and settling during use. The effect of magnetic field on performance of MoS₂ was insignificant. Generally, friction values observed for oil dispersed by MoS₂ showed higher values than that observed for oil and oil dispersed by ZDDP. This performance will be enhanced if the particles are strongly adhered to the contact area and the shear strength of the solid lubricant is less than the adhesion to the substrate. In addition, a film of solid lubricant should be built up of sufficient thickness to cover the contact area completely, and sliding takes place between two smooth oriented layers of lamellar solid lubricant.

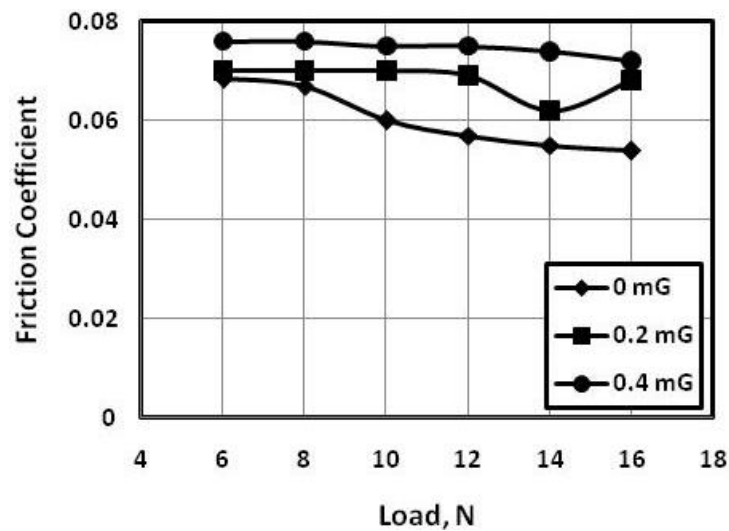


Fig. 5 Friction coefficient displayed by the sliding of steel pin against polyamide disc lubricated by oil dispersed by MoS₂.

CMOC is a copper base additive. Its mechanism of action depends on the selective migration. Copper does not form carbides and also being soft and good heat conductor. The mechanism of action of the CMOC additive is to keep the two contacting surfaces away from each other by forming a protecting layer on the sliding surfaces. The adherence of CMOC particles, which are smaller than 1.0 μm size, into the sliding surfaces is enough strong due their electronic properties, [22]. The degree of adherence of solid lubricant into the sliding surfaces is responsible for the friction and wear reduction. The lubricating action of CMOC depends on the theory of lubrication of the metallic sheets, where copper particles are subjected to a shear stress which will cause plastic flow as soon as it reaches the shear yield strength, which is well known property of copper. The sliding resistance is less than the shear strength of the copper, where friction coefficient cannot exceed the ratio between the shear strength and yield compressive strength. The magnetic field drastically decreased friction coefficient, Fig. 6. It seems that the polarity of CMOC particles strengthened their adherence into the

contact area. Under the action of the magnetic field the force of adhesion significantly increased causing proper surface coating which caused the friction decrease. It should be mentioned that, adhesion force was affected by the electrostatic force generated by friction between steel and polyamide surfaces as well as the magnetic force generated from the magnetic field.

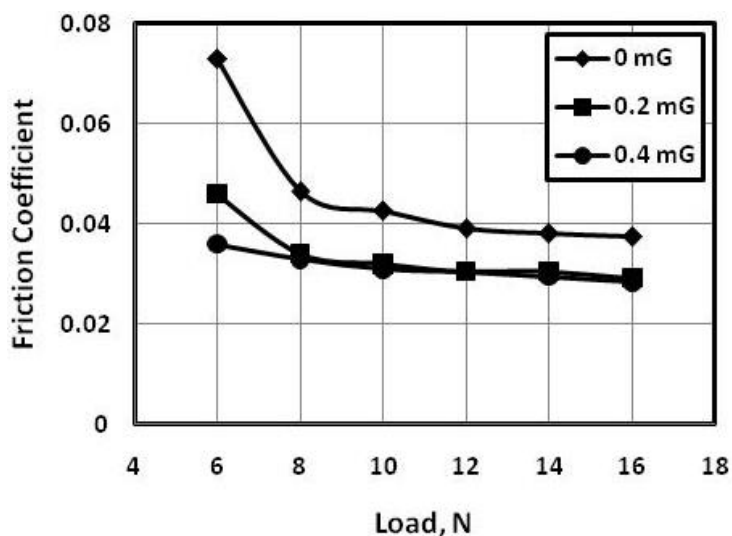


Fig. 6 Friction coefficient displayed by the sliding of steel pin against polyamide disc lubricated by oil dispersed by CMOC.

Friction coefficient displayed by the sliding of steel pin against steel disc lubricated by oil dispersed by C is shown in Fig. 7, where significant friction increase was observed. As already mentioned, not all lamellar solids are capable of interlamellar sliding at low shear stresses. The nature of bonding between the C lamellae is a weak Van der Waals bonding acting between lamellae. The friction increase might be from the relatively high adhesion between lamellae. The lubrication mechanism of C is believed to be a result of the relatively free movement of adjacent layers in these substances. In general, however, C films fail at lower loads and exhibit shorter lifetime than MoS₂ film. The limiting contact stresses for C are a little over half that of MoS₂. Application of magnetic field caused slight friction reduction. This behaviour is attributed to the electronic properties of C. Dispersion of C particles into the oil distributed the electric static charge on the sliding surfaces and consequently adhesion among C particles, polyamide and steel surfaces increased.

Friction coefficient displayed by the sliding of steel pin against steel disc lubricated by oil dispersed by DA showed significant friction decrease, Fig. 8. It seems that the polarity of calcium sulphonate molecules is responsible for the decrease of friction coefficient. Application of the magnetic field might modify the orientation and adherence of the additive particles on the sliding surfaces. Significant reduction in friction coefficient was caused by the magnetic field. As the magnetic field increased friction coefficient decreased. The lowest values of friction coefficient were displayed at the highest value of the magnetic field. The lowest friction coefficient value was 0.023 at 16 N applied load. As a result of the quite good response of DA additive with the magnetic field based on the values of friction coefficient observed for the oil dispersed by

DA additive, it can be recommended to use this additive when the magnetic field is applied.

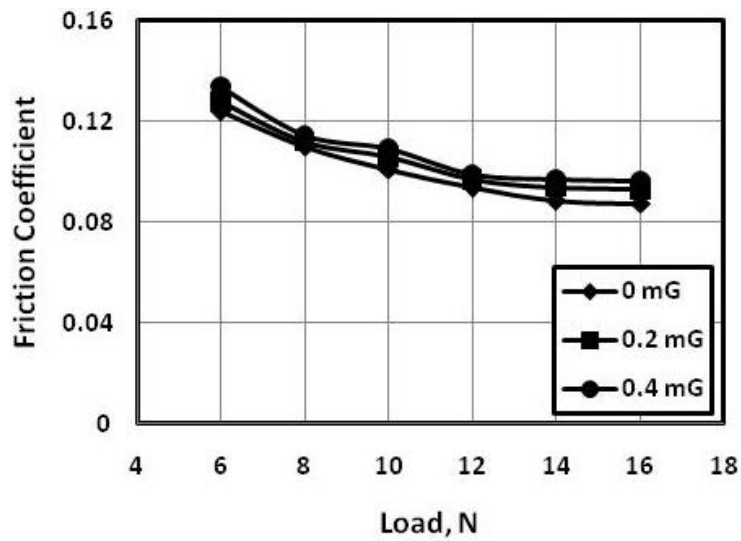


Fig. 7 Friction coefficient displayed by the sliding of steel pin against polyamide disc lubricated by oil dispersed by graphite.

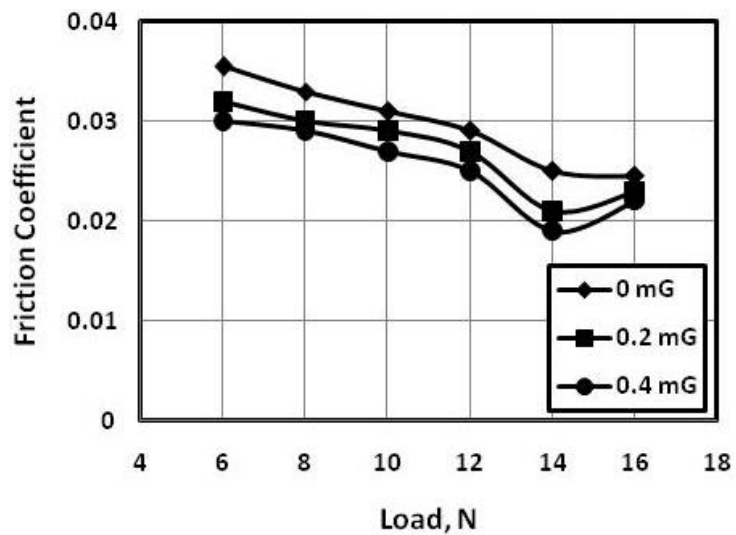


Fig. 8 Friction coefficient displayed by the sliding of steel pin against polyamide disc lubricated by oil dispersed by DA.

The good lubricating properties observed for PTFE additive can be from its ability to form a layer on the sliding surfaces. The very low intermolecular forces of PTFE allow the layer to slide over the friction surface with a minimum of interaction and hence a minimum of friction. PTFE particles dispersed in the oil were much influenced by the magnetic field, Fig. 9, where the lowest value was 0.02 at 0.4 mG magnetic field intensity and 16 N load. The same trend of friction decrease was observed for PMMA particles dispersed in oil, Fig. 10. The values of friction coefficient were relatively higher than that observed for PTFE. Adherence of PTFE into PA surface might be attributed to the relatively high amount of electric static charge generated from PTFE when rubbed both PA and steel, where PTFE gained negative charge and steel as well as polyamide

surfaces gained positive charge. Besides PA surface gained extra positive charge when slid on steel.

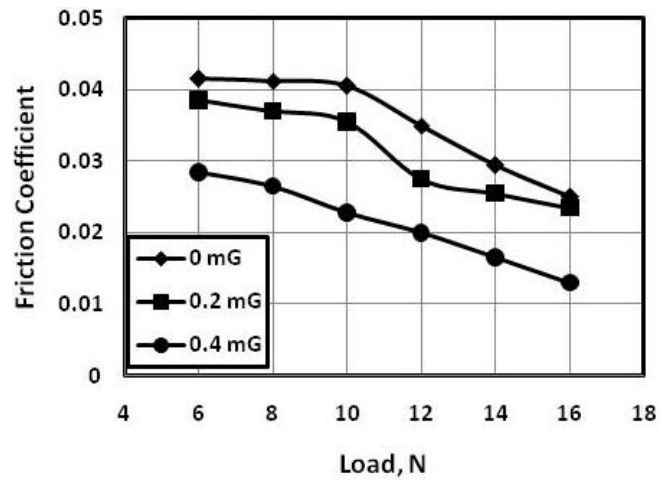


Fig. 9 Friction coefficient displayed by the sliding of steel pin against polyamide disc lubricated by oil dispersed by PTFE.

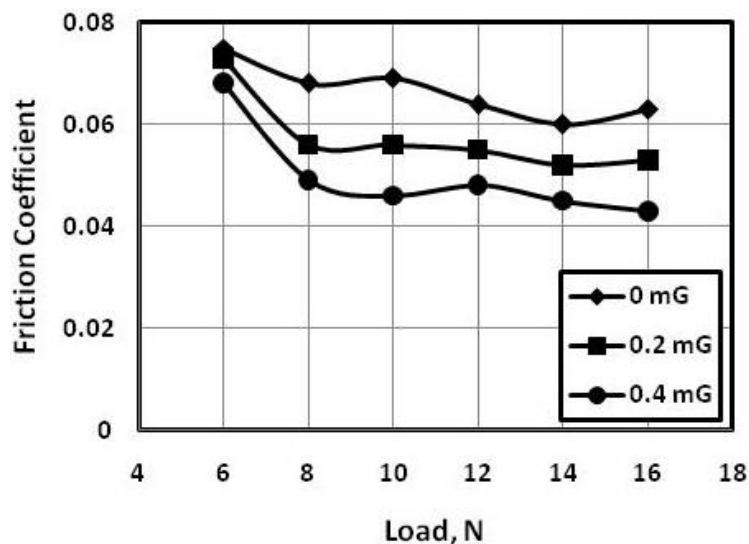


Fig. 10 Friction coefficient displayed by the sliding of steel pin against polyamide disc lubricated by oil dispersed by PMMA.

CONCLUSIONS

1. At surfaces lubricated by paraffin oils friction coefficient decreased with increasing applied load. As the magnetic field increased friction coefficient increased.
2. Dispersing oil by ZDDP additive caused significant decrease of friction. The performance of ZDDP additive was not affected by application of the magnetic field.
3. Dispersing Mo S₂ in the lubricating oil caused significant friction increase, like ZDDP the effect of magnetic field on performance of MoS₂ was insignificant.
4. Magnetic field decreased friction coefficient when the oil was dispersed by CMOC by means of increasing the adherence of CMOC particles into the sliding surfaces due their electronic properties and polarity which strengthened their adherence into the contact area.

Under the action of the magnetic field the force of adhesion significantly increased causing proper surface coating which caused the friction decrease.

5. Like MoS₂ significant friction increase was observed in the presence of C dispersing the lubricating oil. Application of magnetic field caused slight friction reduction. Dispersion of C particles into the oil homogeneously distributed the electric static charge on the sliding surfaces and consequently adhesion among C particles, polyamide and steel surfaces increased.

6. Friction coefficient displayed by oil dispersed by calcium sulphonate showed significant friction decrease due to the polarity of its molecules. Application of the magnetic field caused further friction decrease. As a result of the quite good response of DA additive with the magnetic field based on the values of friction coefficient observed for the oil dispersed by DA additive, it can be recommended to use this additive when the magnetic field is applied.

7. The good lubricating properties observed for PTFE additive can be from its ability to form a layer on the sliding surfaces. PTFE particles dispersed in the oil were much influenced by the magnetic field, where the lowest value was displayed at the highest magnetic field intensity. The same trend of friction decrease was observed for PMMA particles dispersed in oil.

REFERENCES

1. M. El Mansori, F. Pierron, D. Paulmier, Reduction of tool wear in metal cutting using external electromotive sources, *Surf. Coat. Technol.* 163–164 (2003) 472–477.
2. M. El Mansori, V. Iordache, P. Seitier, D. Paulmier, Improving surface wearing of tools by magnetization when cutting dry, *Surf. Coat. Technol.* 188–189 (2004) 566–571.
3. O. Bataineh, B. Klamecki, B.G. Koepke, Effect of pulsed magnetic treatment on drill wear, *J. Mater. Process. Technol.* 134 (2003) 190–196.
4. Y. Iida, T. Stolarski, “Alternation on rolling contact properties of steel due to magnetic field”, *Wear* 266 (2009) 1098–1105.
5. Jiang J., Tian Y., Meng Y., “Role of external magnetic field during friction of ferromagnetic materials”, *Wear* 271 (2011), pp. 2991– 2997
6. Stolarski T. A., Makida Y., “Influence of magnetic field on wear in high frequency reciprocating sliding contacts”, *Tribology International* 44 (2011) 1004–1013
7. Al-Osaimy A. S., “Effect of magnetic field on the performance of vegetable oils dispersed by polymeric particles”, *EGTRIB Journal, Journal of the Egyptian Society of Tribology*, Vol. 8, No. 4, October 2011, pp. 12 – 24, (2011).
8. Abdel-Jaber G. T., Mohamed M. K., Al-Osaimy A. S. and Ali W. Y., "Effect of Magnetic Field on the Performance of Lubricant Additives", September 27 – 29, 2011, Tribologie Fachtagung, Göttingen, Germany, (2011).
9. Mohamed M. K., "Effect of Magnetic Field on the Friction and Wear of Polyethylene Sliding Against Steel", *EGTRIB Journal, Journal of the Egyptian Society of Tribology*, Vol. 5, No. 1, April 2009, pp. 13 – 24, (2009).
10. Abeer A. E., Abo El-Ainin H. M., Khashaba M. I., Ali W. Y., “Effect of Magnetic Field on Friction and Wear of Steel”, *Journal of the Egyptian Society of Tribology*, Vol. 8, No. 2, April 2011, pp. 1 – 15, (2011).
11. Abeer A. E., Abo El-Ainin H. M., Khashaba M. I., Ali W. Y., “Effect of Magnetic Field on Friction and Wear of Brass”, *Journal of the Egyptian Society of Tribology*, Vol. 8, No. 2, April 2011, pp. 16 – 30, (2011).

12. Mahmoud M. M., Mohamed M. K. and Ali W. Y., "Tribological Behaviour of the Contact Surface in the Presence of Electric Current", *IME, Journal of Engineering Tribology*, Vol. 224 No J1 2010, pp. 73 – 79, (2010).
13. Abdel-Sattar S., Alahmady A. and Ali W. Y., "Effect of Magnetic Field on Friction Coefficient Displayed by Rolling Bearings", *EGTRIB, Journal of the Egyptian Society of Tribology*, Vol. 8, No. 3, July 2011, pp. 27 – 39, (2011).
14. Zaidi H., Amirat M., Frene J., Mathia T., Paulmier D., "Magnetotribology of ferromagnetic/ferromagnetic sliding couple", *Wear* 263, pp. 1518 - 1526, (2007).
15. Zaidi H., Senouci A., "Influence of magnetic field on surface modification and friction behaviour of sliding couple aluminium/XC48 steel", *Surf. Coat. Technol.* 120 - 121, pp. 653 - 658, (1999).
16. Chin K. J., Zaidi H., Mathia T., "Oxide film in magnetized sliding steel/steel contact analysis of the contact stress field and film failure mode", *Wear* 259, pp. 477 - 481, (2005).
17. Hongjun J, Yonggang M, Shizhu W, Wong PL, "Active control of friction by applying electric fields across boundary films of stearate", *Proceedings of ASIATRIB'98, Beijing, China*, pp. 755–60, (1998).
18. El Mansori M., Schmitt M., Paulmier D., "Role of transferred layers in friction and wear for magnetized dry frictional applications", *Surface and Coatings Technology* 108–109, pp. 479–483, (1998).
19. M. El Mansori, E. Csapo, H. Zaidi, D. Paulmier, "Study of magnetized steel XC48/graphite couple in the sliding contact", *Nordtrib 96, 7th Nordic symposium on tribology, Bergen, Norway*, Vol. III, (1996).
20. Morizur, M. F. and Briant, J., "Modifications of Electron Properties of Friction Surfaces in Boundary Lubrication", *C2/4/87, IMechE*, (1987).
21. Taylor, C. M., "Engine Tribology", *Tribology Series*, 26, Elsevier, Amsterdam, pp. 76, (1993).
22. Yamamoto, Y., Ono, B. and Ura, A., "Effect of Applied Voltage on Friction and Wear Characteristics in Mixed lubrication", *Proceedings of the VI Int. Congress on Tribology*, Vol. 5 *EUROTRIB'93*, Budapest, Hungary, pp. 82 - 89, (1993).
23. Nery, H., Zaidi, H., Pan, L. and Paulmier, D., "Influence of Magnetic Field on Steel in Sliding Contact", *Proceedings of the VI Int. Congress on Tribology*, Vol. 5 *EUROTRIB'93*, Budapest, Hungary, pp. 70 - 75, (1993).